

A novel method for controlled synthesis of nanosize hematite (α -Fe₂O₃) thin film on liquid-vapor interface

Pawan Kumar¹, Raj Kumar Singh², Nitin Rawat³, Partha Bir Barman,¹ Subhash Chander Katyal⁴, Hwanchol Jang³, Heung-No Lee^{3*}, and Rajesh Kumar^{1,3*}

¹Jaypee University of Information Technology, Wanknaghat, Solan (H.P) -173234, India

²CSIR-Indian Institute of Petroleum, Dehradun - 248005, India

³Gwangju Institute of Science and Technology, Gwangju - 500712, Republic of Korea

⁴Jaypee Institute of Information Technology, Sector 128, Noida (U.P) - 201304, India

*Corresponding author address:

E-Mail: rajesh.kumar@juit.ac.in, rajeshkumarf11@gmail.com, heungno@gist.ac.kr

Tel.: +91 -1792 -239386

Fax: +91 -1792-245362

Abstract

Hematite (α -Fe₂O₃) films having high quality surface morphology have been formed at the liquid-vapor interface using a novel approach. The surface morphology/size of the nanoparticles constituting the film is tuned in a controlled manner. It is observed that the concentration of polyvinyl alcohol (PVA) in the precursor Fe³⁺/Fe²⁺ solution, the concentration of ammonia (NH₃) vapor, and the annealing temperature are factors influencing the surface morphology/size of nanoparticles. The diameter of the α -Fe₂O₃ nanoparticles inside the film is controlled to be 2 nm to 15 nm by varying the synthesis conditions, and accordingly, the films have roughness in the 1.34–6.8 nm range. The prepared α -Fe₂O₃ films are crystalline in nature and exhibit superparamagnetic behavior at room temperature.

Keywords:

α -Fe₂O₃ nanoparticles, NH₃ vapor, concentration of PVA, annealing temperature.

Introduction

Iron oxides attract interest as materials because of their catalytic, magnetic, and semiconducting properties (Aronniemi et al. 2004; Chandra et al. 2010). The material α -Fe₂O₃, iron oxide in particular has been suggested for application as a catalyst (Liu et al. 2007), a magnetic material (Wu et al. 2006), a photo catalyst (Chirita et al. 2009), an anode in Li-ion batteries (Ryu et al. 2010), in photo electrochemical solar cells (Shinde et al. 2011; Ahmmad et al. 2010), a water splitter (Shen et al. 2012), in non-linear optics (Zhou et al. 2000), and for gas sensors (Gou et al. 2008; Zhang et al. 2011).

For any technological application, the size of the α -Fe₂O₃ nanoparticles composing a film is an important factor. The small size of α -Fe₂O₃ nanoparticles provide a large surface area for adsorption/desorption of the chemical species in contact with it, thus allowing for good performance of the application device using the film. Most of the properties such as superparamagnetism (Lindgren et al. 2002; Ramachandran et al. 2007), light absorption (Mulmudi et al. 2011), Li-ion adsorption (Turkovoć et al. 2011; Jin et al. 2012), optical limiting (Singh et al. 2008), and gas sensing (Aronniemi et al. 2008) depend upon the size of α -Fe₂O₃ nanoparticles. The size of α -Fe₂O₃ nanoparticles depends upon the synthesis methods (Dong et al. 2012) as well. So far, many methods of synthesizing α -Fe₂O₃ films such as chemical vapor deposition (CVD) (Mathur et al. 2006; Ge et al. 2009; Chatzitheodorou et al. 1986), reactive ion beam sputtering (Birkholz et al. 1992), laser assisted CVD (Sivako et al. 2005), and ultrasonic spray pyrolysis (Cesar et al. 2006; Fu et al. 2003; Jia et al. 2005; Mahapatra et al. 2009; Park et al. 2009; Miller et al. 2004; Zang et al. 2010; Kay et al. 2006; Glasscock et al. 2007; Kim et al. 2011) have been reported. Also a well known vapor-liquid-solid (VLS) method (Liu et al. 2007; Hwang et al. 2009) has also been used to synthesize α -Fe₂O₃ (Kumar et al. 2009). Nevertheless, most of them are not cost effective and lack the flexibility of formation and transformation of the film on a desired substrate.

Methods employing polymers have also been reported (Morishita et al. 2005; Omi et al. 2001; Liu et al. 2007). These methods combine different polymers, utilizing their emulsion forming tendency and adsorption/encapsulation property of metal oxide nanoparticles into their dispersed polymeric micro and nanospheres. In most of the methods, a polymer such as PVA is frequently used in the synthesis of magnetic nanocomposites as it is a unique, synthetic, nontoxic, biocompatible, water-soluble, and easily available polymer. Also it has a large number of -OH groups for interaction, which is a strong reason for its utilization.

Here, we present a novel approach for the formation of α -Fe₂O₃ film using PVA polymer in the precursor solution. Initially, a PVA composite film was formed on the liquid-vapor interface, which after transferring over a glass substrate and annealing in a furnace, was converted to an α -Fe₂O₃ film. In this work, tuning the size of nanoparticles/surface morphology as well as flexibility of transferring the film that is formed at the liquid-vapor interface to a desired substrate has been achieved. By changing the synthesis parameters, such as concentration of NH₃ vapor, film annealing temperature, and concentration of PVA, films of different morphologies have been formed. The method presented here is a comparatively low temperature method for the formation of α -Fe₂O₃ film.

Experimental

Material Synthesis

In order to make a precursor solution, $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ (purity 99.99%), as a source of Fe^{3+} ions, and FeCl_2 (purity 99.99%), as a source of Fe^{2+} ions, were purchased from Sigma Aldrich. NH_3 solution (conc. 25%) was purchased from E. Merck. The host polymer polyvinyl alcohol (molecular weight =125000) was purchased from S. D. Fine Chemicals Limited, India.

Method

A precursor solution with 24 mM FeCl_2 and 22 mM $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ was initially prepared. Then a measured amount, as mentioned in the following discussion, of PVA was added to the precursor solution. The solution was stirred for 10 minutes at 80°C and immediately transferred to a petri dish placed in an argon (Ar) chamber as shown in Fig. 1. Then a measured volume of NH_3 vapor was poured through a syringe into the chamber containing the solution in the petri dish. After pouring NH_3 vapors, the chamber was kept sealed for 10 minutes to facilitate the chemical reaction between NH_3 vapor and the PVA containing precursor at the surface of the solution. Consequently, the liquid-vapor interface converted into a thin floating film. The obtained film was transferred to the surface of distilled water filled in another petri dish. The film was then deliberately transferred to the surface of a glass substrate.

The above experiment was repeated in order to observe the effect of NH_3 vapor concentration on the film morphology. The films were formed by using 4%, 6%, and 8% volume of NH_3 in the reaction chamber. Similarly, a second set of films were formed by varying the concentration of PVA in the precursor solution. The PVA concentrations were 16 μM , 32 μM , and 64 μM while 6% volume of NH_3 vapor was used inside the chamber. Then, in order to form $\alpha\text{-Fe}_2\text{O}_3$ films, the films obtained in the above experiments were annealed at 500°C for 2 hours in an Ar gas environment. We also performed an experiment to study the effect of annealing temperature on surface morphology. For this experiment, the films were formed using 6% of NH_3 vapor and 32 μM of PVA. The film was annealed at temperatures of 250°C and 500°C respectively, for 2 hours in Ar gas environment.

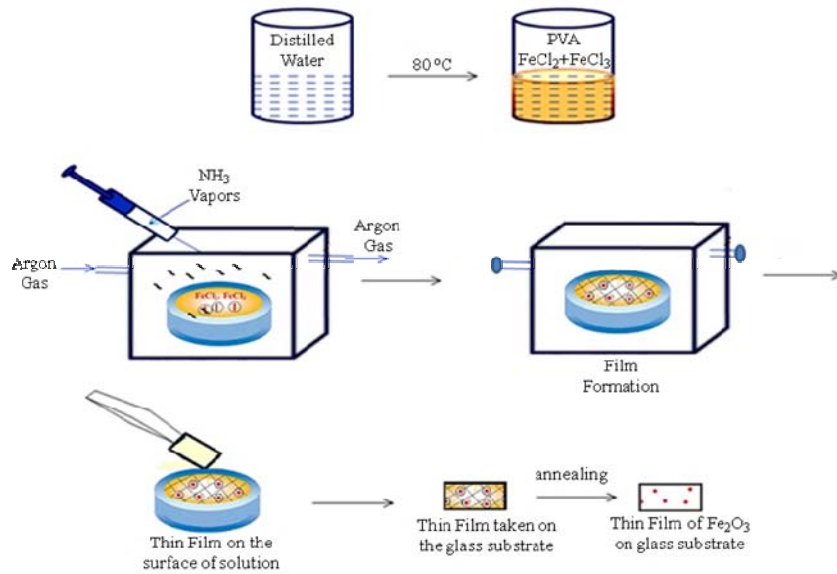


Fig. 1 Schematic illustration of nanosized hematite ($\alpha\text{-Fe}_2\text{O}_3$) film formation on a liquid-vapor interface.

Microstructural and Magnetic Characterization

Scanning electron microscopy (SEM), transmission electron microscopy (TEM), energy dispersive X-ray spectroscopy (EDX), atomic force microscopy (AFM), and X-ray diffraction (XRD) techniques have been used for the structural characterization of the films and to study their morphology. Magnetic characterization has been carried out using the vibrating sample magnetometer (VSM) and magnetic property measurement system (MPMS).

Results and discussion

Mechanism of nanosized hematite ($\alpha\text{-Fe}_2\text{O}_3$) film formation

In $\text{Fe}^{3+}/\text{Fe}^{2+}/\text{PVA}$ system, the possible mechanism of the film formation on liquid-vapor interface is via the encapsulation or adsorption of $\text{Fe}^{2+}/\text{Fe}^{3+}$ ions on the PVA chain. The bonding between $\text{Fe}^{2+}/\text{Fe}^{3+}$ and PVA may have occurred due to the interaction of PVA hydroxyl groups with the hexaaquairon complex species, because it is well known that chloride salts of Fe^{2+} and Fe^{3+} form octahedral hexaaquairon complexes in water. One of the complexes of Fe^{3+} is shown in Fig. 2.


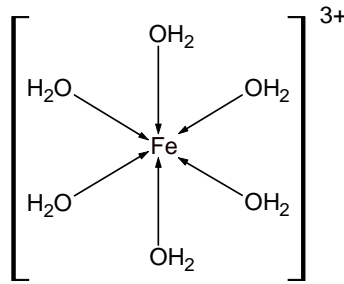


Fig. 2 Structure of $[\text{Fe}(\text{H}_2\text{O})_6]^{3+}$ complex formed by Fe^{3+} in aqueous solution.


Here, each of the six water molecules are attached to the central Fe^{3+} ion via a coordinate bond using one of the lone pairs on the oxygen. The hydrogen atoms attached to the water ligands are sufficiently positive and they can be pulled off in a reaction involving water molecules in the solution. Here the water molecule works as a weak base.



Further, loss of hydrogen ions may also take place as well, from a second and a third water molecule resulting into the final neutral insoluble form, i.e., $[\text{Fe}(\text{H}_2\text{O})_5\text{OH}_3]$.



Fe^{2+} also forms a similar type of water coordinated species. The added PVA can form hydrogen bond between its -OH groups present in its chains with these aqua iron complex species. If the hydroxyl groups from the different PVA chains take part in hydrogen bonding then it may also lead to PVA cross linking (Lin et al. 2003). So using this mechanism, the $\text{Fe}^{2+}/\text{Fe}^{3+}$ ions in the solution may be encapsulated in the polymer chain. When the NH_3 vapor is poured into the reaction chamber, these adsorbed or encapsulated $\text{Fe}^{2+}/\text{Fe}^{3+}$ ions get converted into the nanoparticles of Fe_3O_4 , in accordance with the following reaction:



Due to the increased pH value of the solution, co-precipitation of Fe_3O_4 takes place through substantial PVA cross linking and solidification resulting in the formation of a thin film over the surface of the solution. If a higher concentration of NH_3 is available, the reaction on the surface will be faster and it will lead to the formation of a thick film. Moreover, a higher concentration of the NH_3 vapor will cause diffusion to the solution beneath the surface layer so that a further thicker film with agglomerated nanoparticles will form. When the $(\text{Fe}_3\text{O}_4)/\text{PVA}$ nanocomposite film is annealed after transferring onto a glass substrate, the organic PVA matrices evaporate and Fe_3O_4 oxidizes to form $\alpha\text{-Fe}_2\text{O}_3$. Hence, after annealing, the glass substrate remains coated with a film of $\alpha\text{-Fe}_2\text{O}_3$ nanoparticles.



Simultaneously, the formation of $\alpha\text{-Fe}_2\text{O}_3$ may also take place according to the following reaction:



Effect of NH₃ concentration

The precursor solution was exposed successively to three concentrations viz. 4%, 6%, and 8% of NH₃ vapors. Then the obtained films after their transfer to the glass substrate were annealed for 2 hours at 500°C in a horizontal tube furnace in an Ar gas environment. SEM images of the annealed films are shown in Fig. 3. In the SEM images, a slight variation in the size of the particles with the increase in concentration of the NH₃ vapor in the reaction chamber can be observed. The films obtained for 4% and 6% vapors of NH₃ are composed of nanoparticles having diameters of about 10 nm (Fig. 3a and 3b). The film obtained for 8% of NH₃ vapor, although possesses nanoparticles having diameter of about 10 nm, has nanoparticles in the aggregated form as shown in the inset of Fig. 3c. Therefore, due to the increase in concentration of NH₃ vapor, aggregation of the nanoparticles takes place that causes surface roughness of the films but there is no change in the phase and composition of the films on varying the NH₃ concentration. The root mean square (*rms*) surface roughness of these films was measured by AFM. Other than the surface roughness caused by the variation in the percentage of NH₃ vapor, some small cracks are also observed. These cracks are either thermal induced cracks (Glasscock et al. 2008) or have been produced by the stress induced during the transfer of the films from the surface of the liquid to the surface of the substrate as observed in the SEM images (Fig. 3a and 3b). For the film formed at moderate concentration viz. 6% of NH₃ vapor concentration, XRD characterizations were used. The XRD pattern shown in Fig. 3d corresponds to the heated and unheated films formed at 6% of NH₃. In the XRD pattern, the annealed sample contains the peaks at 2θ (32.3 and 35.4). These peaks are in accordance with the Joint Committee on Power Diffraction Standards [JCPDS, file no. 89-8104], and corresponds to α -Fe₂O₃. The particle size has also been calculated using Scherer formula $d = 0.94\lambda / \beta \cos\theta$, where λ is the wavelength of the X-ray used. The calculated particle size of 20 nm is close to the particle diameter observed in the SEM image.

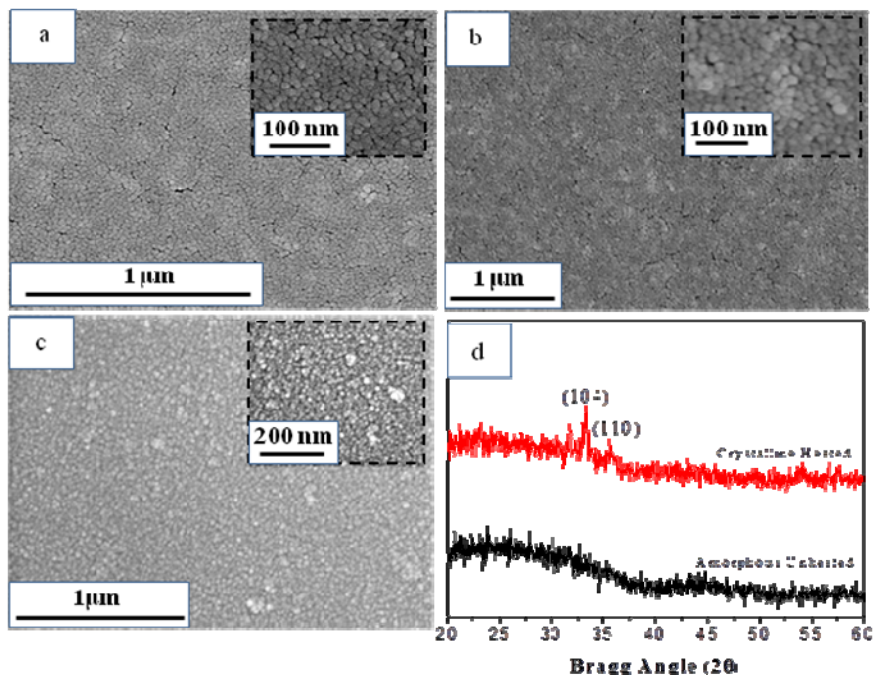


Fig. 3 shows the SEM and XRD pattern of the films. The SEM image for (a) 4% NH₃ vapor, (b) 6% NH₃ vapor, and (c) 8% NH₃ vapor. The XRD pattern of the unheated film and annealed film at 500°C for 2 hours using 32 μM concentration of PVA and 6% NH₃ vapor is shown in (d).

For the TEM characterization, the films formed on the surface of the solution were transferred directly on a carbon coated TEM copper grid. Figure 4a shows a TEM image of the film formed for 4% vapor of NH₃, and annealed at 500°C for 2 hours. Here almost a uniform size of the α-Fe₂O₃ nanoparticles ranging from 10 nm to 15 nm can be observed. There is a small clustering of the nanoparticles and the film possesses a uniform distribution of α-Fe₂O₃ nanoparticles. Further, the film was characterized by AFM for surface morphology and roughness.

Figures 4b and 4c are the AFM images of the film obtained for 4% NH₃ vapor. The root mean square (*rms*) roughness is 1.34 nm as obtained from the AFM analysis.

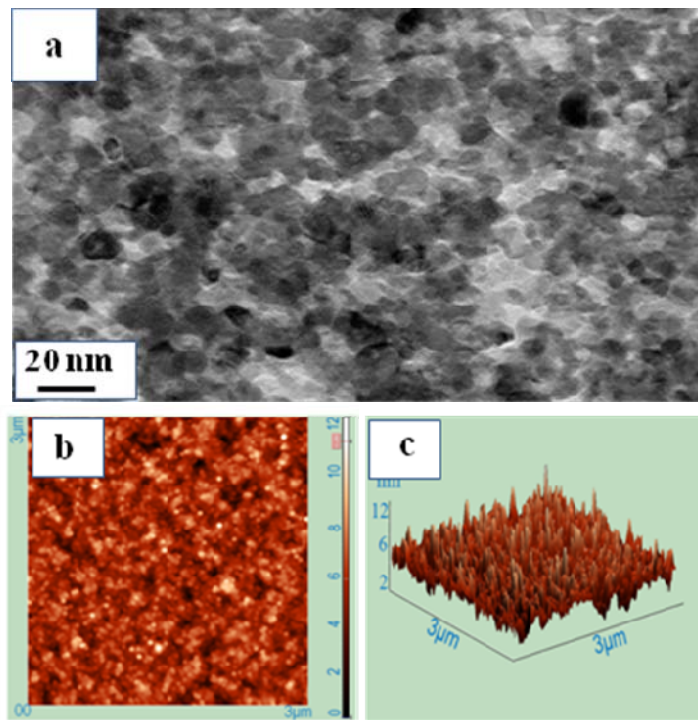


Fig. 4 (a) is the TEM image of the film formed for 4% NH₃ vapor and 32 μM concentration of PVA. (b) is an AFM amplitude image and (c) is the three dimensional AFM image of the film.

For 6% NH₃ vapor, although the diameter of nanoparticles remains between 10 nm and 15 nm, their aggregation starts as shown in the TEM image in Fig. 5a. The aggregation is also observed in the AFM image as shown in Fig. 5b. In this case, the roughness of the film increases to 4.5 nm as measured using AFM data of Fig. 5c.

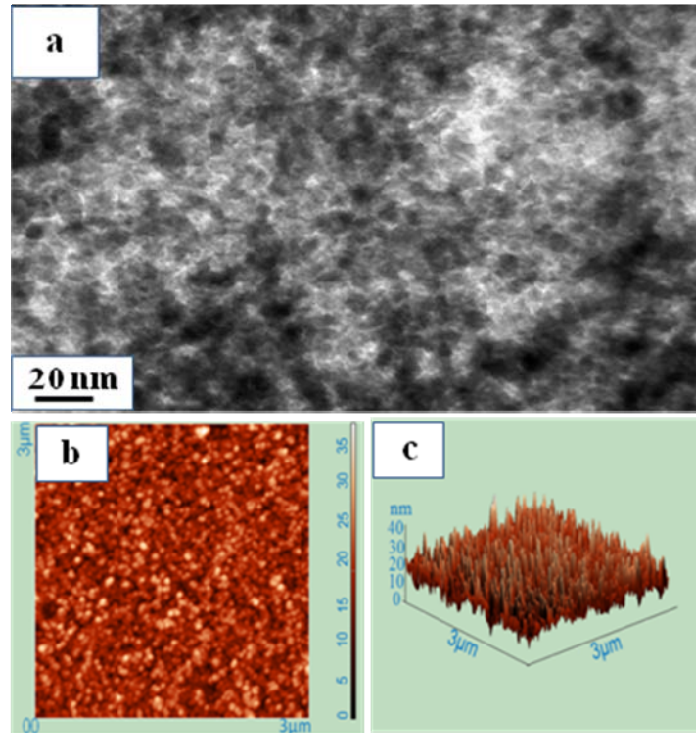


Fig. 5 (a) is the TEM image of the film formed for 6% NH_3 vapor and 32 μM concentration of PVA. (b) is an AFM amplitude image and (c) is the three dimensional AFM image of the film.

For 8% NH_3 vapor, the aggregation of nanoparticles increases further as shown in Fig. 6a to 6c and the whole film becomes thicker. By closely inspecting the images, the size of the nanoparticles inside the aggregate is found to be almost 10 nm. Also the dark region in the TEM image (Fig. 6a) indicates the thickness of the film. Again, the roughness of the film also increases to 6.8 nm as observed in AFM measurements. Therefore, at higher percentages of the NH_3 vapor, thickness of the film increases. The increase in the thickness of the film is due to the formation of a large number of nanoparticles on the surface of the solution for higher NH_3 percentages. A higher percentage of NH_3 vapor makes more NH_3 molecules available at the surface of the solution and changes the pH value at the surface rapidly, resulting in a relatively larger co-precipitation on the surface. The overall effect of higher concentration of NH_3 is the formation of thick film on the liquid-vapor interface.

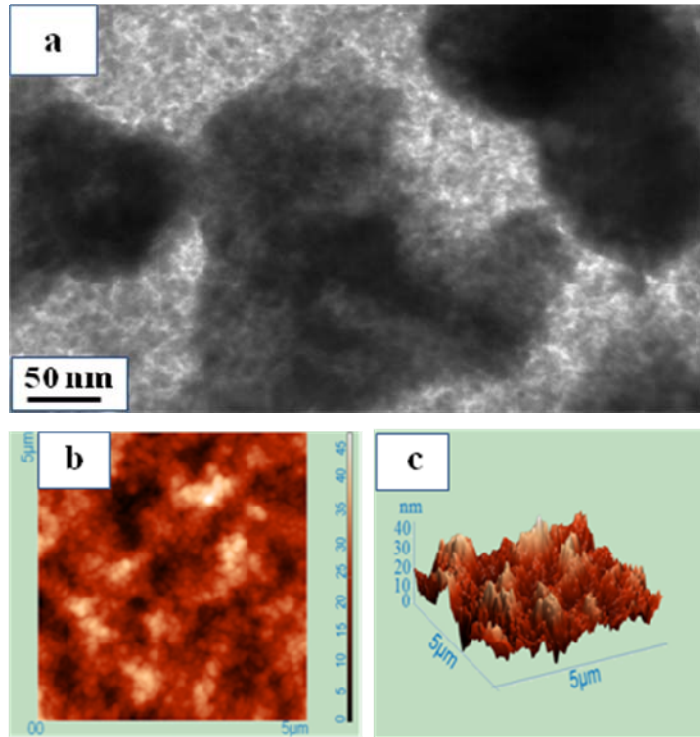


Fig. 6 (a) is the TEM image of the film formed for 8% NH_3 vapor and 32 μM concentration of PVA. (b) is an AFM amplitude image and (c) is the three dimensional AFM image of the film.

Effect of PVA concentration

In the second case, the experiment was carried out by using 16 μM , 32 μM , and 64 μM concentrations of PVA in the precursor solution. For 16 μM concentration, the size of the nanoparticles composing the film is about 25 nm as shown in Fig. 7a. When we increased the PVA concentration to 32 μM , the size of the nanoparticles reduced to 10 nm as shown in Fig. 7b. On further increasing the PVA concentration to 64 μM , aggregated nanoparticles are observed. The possible reason that leads to reduction in the size of nanoparticles with increase of PVA is the capping effect of PVA. The increased concentration of PVA caps the surface of nanoparticles, which prevents their growth due to polymeric stabilization. For a PVA concentration of 64 μM , the particles are in the cluster form as shown in SEM image (Fig. 7c) where the cluster is formed by the clustering of the small nanoparticles. Thus the big particles are formed by the aggregation of the small nanoparticles. Therefore, it can be stated that the aggregation of the nanoparticles starts as the concentration of PVA reaches 64 μM in the precursor solution. Due to the small size of the nanoparticles formed for PVA concentration of 64 μM , the particles have higher surface energy. As soon as the temperature is increased to 500°C the PVA evaporates and the small nanoparticles aggregate to reduce their surface energy. So the particles are observed in the aggregated form for higher concentrations of PVA.

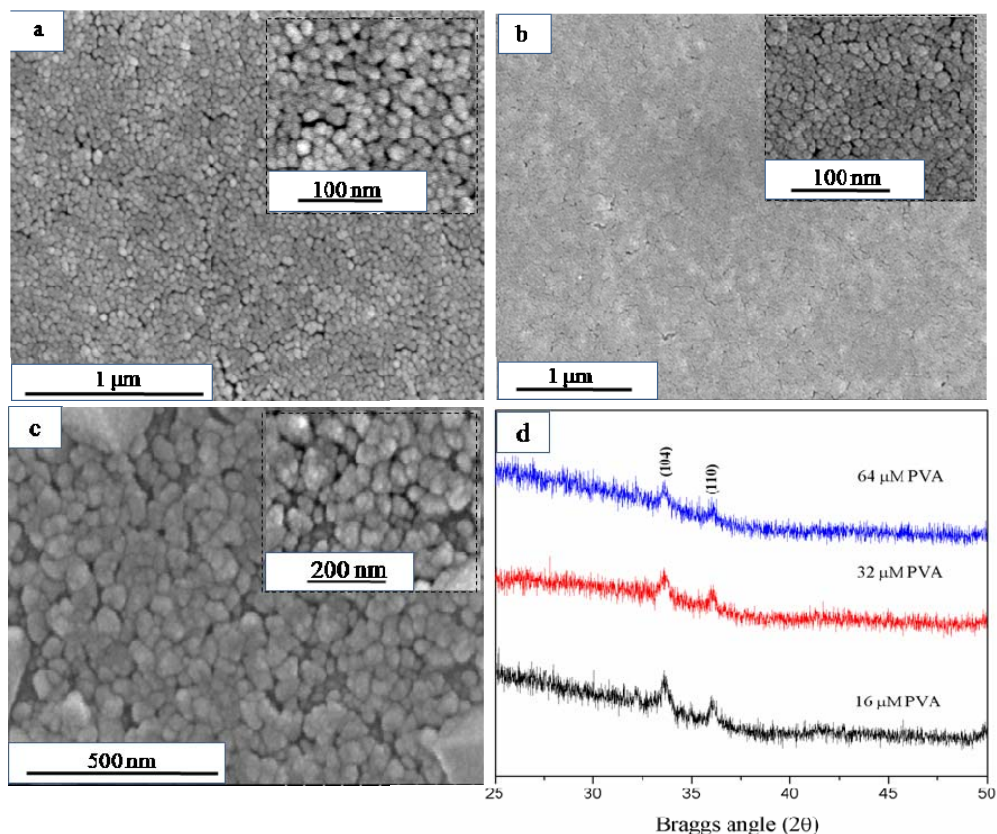


Fig. 7 represents the SEM image of the films formed for (a) 16 μM , (b) 32 μM , and (c) 64 μM of PVA concentration at 6% NH_3 vapor. (d) shows XRD patterns of the film for different PVA concentration.


Figure 7d shows the XRD spectrum of films formed for 16 μM , 32 μM , and 64 μM concentration of PVA. In the XRD pattern only two peaks at 2θ equal to 33.2° and 35.9° are observed that correspond to $\alpha\text{-Fe}_2\text{O}_3$. Therefore, from the XRD pattern it can be concluded that with the change of PVA concentration there is no change in the phase of the film contrary to the reported study (Uekawa et al. 1998) in which they observed a change in phase probably due to the large concentration of PVA. In this study, in the XRD pattern only the intensity of the peaks changes due to the change in the size of particles, smaller nanoparticles are formed inside the film for large concentrations of PVA. The particle size is calculated by using Scherrer formula, the lattice constants corresponding to the PVA concentrations are given in table 1. The $\alpha\text{-Fe}_2\text{O}_3$ exhibits a rhombohedral corundum structure and the corresponding lattice constant values are in agreement with the reported data (Sahoo et al. 2010).

Table 1. Calculated particle size and lattice parameter a, b and c from the XRD data for film formed for 16 μM , 32 μM and 64 μM concentration of PVA.

PVA concentration (μM)	d (nm) from XRD data	a = b (\AA)	c (\AA)
16	18.43435	4.97	13.55
32	12.56788	4.97	13.56
64	12.38128	4.98	13.53

Effect of annealing temperature

The films in this study were formed using a moderate concentration of PVA viz. $32 \mu\text{M}$ in the precursor solution. Figure 8a shows a TEM image of the unheated film, which is an amorphous structure. Also, in the corresponding XRD pattern shown in Fig. 8f, no crystalline peak is observed, which confirms the amorphous nature of the film. For the film annealed at 250°C no peak is observed due to the amorphous nature of the film. For elemental composition, EDX analysis has been done during TEM analysis. The EDX spectrum of unheated film is shown in Fig. 8d. In the EDX analysis the elements Fe and O are found to be in the atomic ratio 37.20:50.72 which corresponds to Fe_3O_4 . To observe the effect of annealing temperature, the films were annealed for 2 hours respectively, at 250°C and 500°C . The annealing of the films was carried out in a horizontal tube furnace in an Ar gas environment.

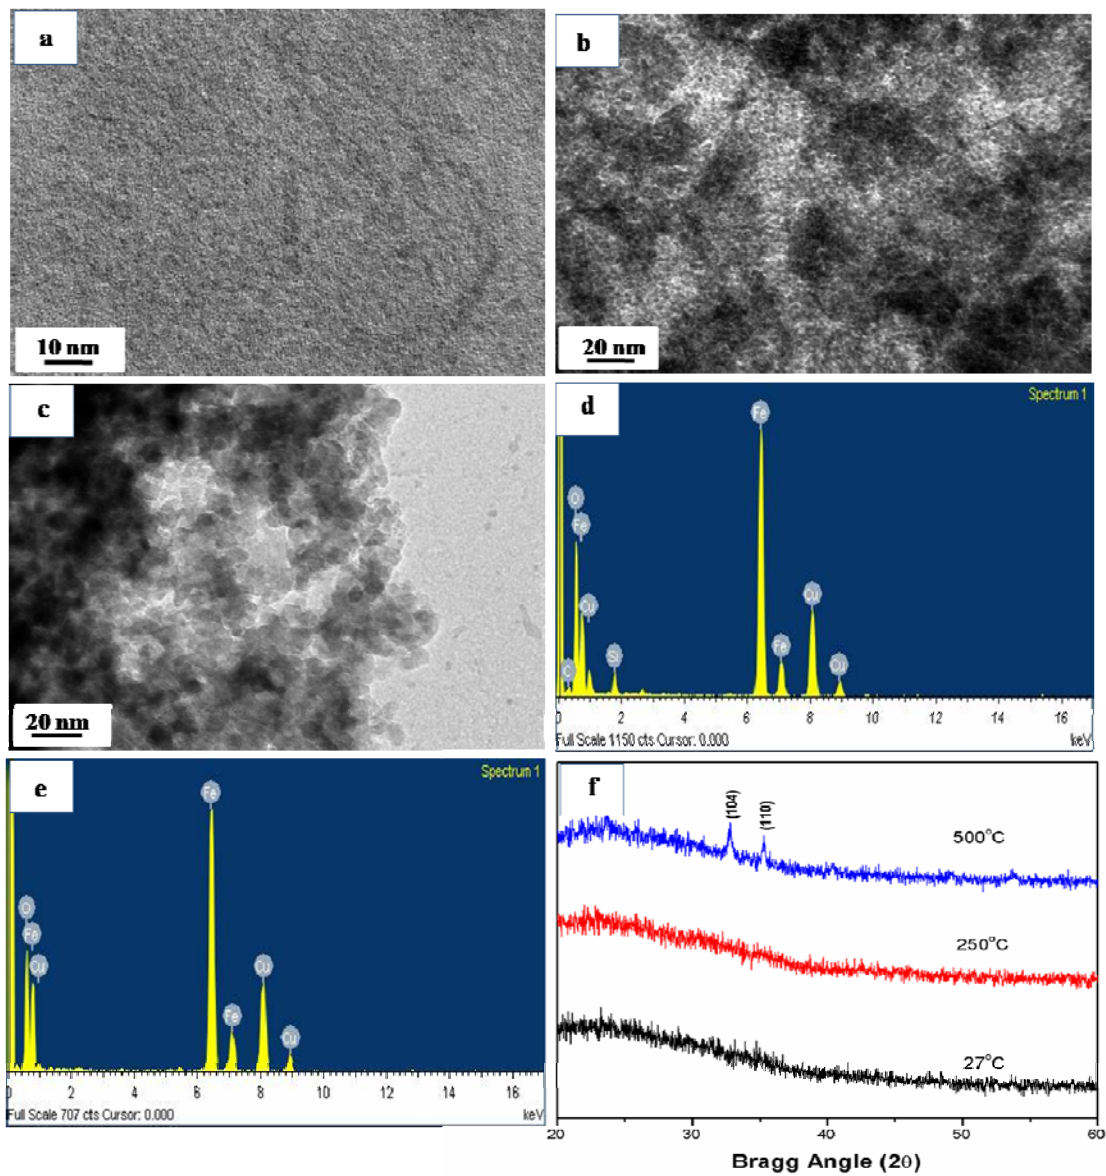

Figs. 8 (a), (b) and (c) are TEM images of unheated and annealed films at 250°C and 500°C temperatures respectively. (d) is EDX of the unheated film and (e) is EDX of the film annealed at 500°C temperature. (f) is the XRD pattern of the unheated film, and films annealed at temperatures of 250°C and 500°C for 2 hours. All the films have been formed for 32 μ M PVA concentration at 6% of NH_3 vapor.

Figure 8b represents a TEM image of the film annealed at 250°C for 2 hours. In this film nanoparticles of diameter less than 5 nm can be observed. Through the XRD study, we find that the crystalline nanoparticles are formed inside films that are annealed above 250°C. This may be due to the fact that when the film is heated at 250°C, the PVA evaporates and the amorphous $\alpha\text{-Fe}_2\text{O}_3$ starts to crystallize into small $\alpha\text{-Fe}_2\text{O}_3$ nanoparticles. Further, the annealing temperature was increased to 500°C. The TEM image shown in Fig. 8c is the resultant film formed after annealing at 500°C for 2 hours. Here the film contains crystalline nanoparticles having an average diameter of about 10 nm. The crystalline nature has also been detected in XRD (Fig. 8f). This indicates that an increase in the annealing temperature increases the size of the $\alpha\text{-Fe}_2\text{O}_3$ nanoparticles inside the film. While analyzing the film formed after annealing at 250°C and 500°C, using EDX, almost a similar elemental composition has been observed. Figure 8e shows the EDX spectrum of the film annealed at 500°C. Here the elements Fe and O are in the ratio 32.98:49.19 forming Fe_2O_3 . Thus, by changing the annealing temperature, the size of the nanoparticles inside the film can be varied, which then directly alters the surface area for the adsorption, and its efficiency in applications of $\alpha\text{-Fe}_2\text{O}_3$ films such as in solar cells, gas sensors, Li-ion batteries, and optical limiting can be improved.

Magnetic study

The $\alpha\text{-Fe}_2\text{O}_3$ exhibits weak ferromagnetism above 260K and antiferromagnetism below 260K (Pastor et al. 2012). The transition temperature between antiferromagnetic and ferromagnetic is termed as Morin transition (T_m) temperature. The observed weak ferromagnetism arises from the canting of the antiferromagnetically align spins above T_m . Nanoparticles of $\alpha\text{-Fe}_2\text{O}_3$ phase also exhibits this behavior and the Morin temperature has been found to be strongly dependent on the size of the $\alpha\text{-Fe}_2\text{O}_3$ particles; generally it decreases with the decreasing size of the nanoparticles and it tends to disappear below a diameter of ~ 8 nm for spherical particles (Mansilla et al. 2002) even for 32 nm $\alpha\text{-Fe}_2\text{O}_3$ nanoparticles for which a suppression of Morin temperature has been reported (Bhowmik et al. 2010).

Field cooled (FC) and zero field cooled (ZFC) studies have been carried out by applying a magnetic field of $H=100$ Oe to observe the effect of temperature on magnetization of the films that were annealed at 100°C, 250°C, and 500°C temperatures; the magnetization versus temperature (M-T) plots are shown in Figs. 9a to 9c. In the M-T plots, a continuous increase in the magnetization of the films with decreasing temperature is observed, indicating suppression of the Morin transition. The increase in the magnetization with the decrease of temperature suggests an increase in superparamagnetic/paramagnetic contribution of uncompensated surface spin in antiferromagnetic grains (Bhowmik et al. 2004). Therefore, although the particle size increases with the annealing temperature, the size of nanoparticles is too small to observe the Morin transition (Mansilla et al. 2002) even for the film annealed at 500°C. For the films annealed at temperatures of 100°C, 250°C, and 500°C, the M-H measurement at room temperature was

also carried out using the VSM technique. The samples annealed at 100°C, 250°C, and 500°C show a superparamagnetic behavior as shown in Fig. 9d. For these samples the saturation magnetizations are 30.71 emu/cm³, 35.17 emu/cm³, and 42.78 emu/cm³, respectively.

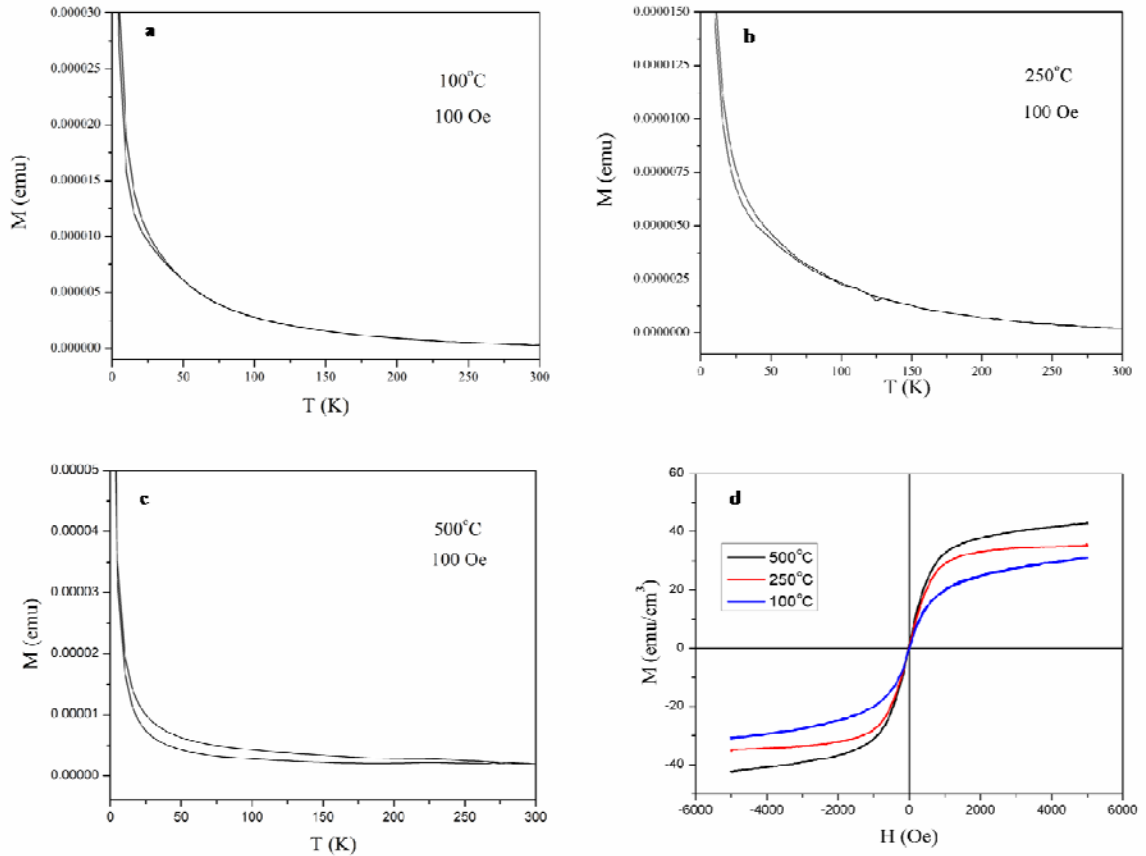


Fig. 9 represents M-T plot of the α -Fe₂O₃ films annealed at (a) 100°C, (b) 250°C, and (c) 500°C temperatures. (d) is the M-H plot of these films at room temperature.

The observed saturation magnetization of 30.71 emu/cm³, 35.17 emu/cm³, and 42.78 emu/cm³, respectively for the α -Fe₂O₃ films annealed at 100°C, 250°C, and 500°C temperatures are much higher than that of the bulk value (~1 emu/cm³) of α -Fe₂O₃. Although, in XRD no peak was detected corresponding to the gamma phase (γ -Fe₂O₃) formation but from the observed higher values of magnetization on the films it is inferred that during the annealing a ferromagnetic gamma phase (γ -Fe₂O₃) also forms within a small fraction inside the film. Since the γ -Fe₂O₃ has a higher magnetic moment (430 emu/cm³) as compared to α -Fe₂O₃, a small fraction γ -Fe₂O₃ inside the film is enough to enhance its saturation magnetization. Using standard values of the magnetization (bulk values) of the two phases, i.e., 1 emu/cm³ for α -Fe₂O₃ and 430 emu/cm³ for γ -Fe₂O₃, the concentration of the γ -Fe₂O₃ inside the film has been estimated using the formula $M_s = (x)(M \text{ of } \alpha \text{ Fe}_2\text{O}_3) + (1-x)(M \text{ of } \gamma \text{ Fe}_2\text{O}_3)$. Here M_s is the observed total magnetization of the sample. We obtained 7.5%, 8.2%, and 10% of γ -Fe₂O₃ phase ($1-x = 0.075, 0.082$ and 0.01) in

the film annealed at temperatures of 100°C, 250°C, and 500°C, respectively alongside the remaining alpha phase nanoparticles. It may be noted here the percentage of γ -Fe₂O₃ phase has been calculated by using the bulk values of magnetization, however in antiferromagnetic nanoparticles the saturation magnetization could be higher than their bulk values due to the canting and uncompensated surface spins. Therefore, while considering the canting and uncompensated surface spins the percentage of γ -Fe₂O₃ phase would reduce correspondingly.

The observed room temperature superparamagnetic behavior of the films follows the Langevin function $M(H/T) = M_0 [\coth (M_0 m H / k_B T) - k_B T / M_0 m H]$, (Parvin et al. 2004) as shown in Fig. 10, where M_0 is the saturation magnetization and m is the mass in grams of the individual particle. Taking the density of the material to be 5.2 g/cm³, from the Langevin fit curves for the films annealed at 100°C, 250°C, and 500°C, the calculated values of M_0 are 33.5 emu/cm³, 36.8 emu/cm³, and 44.0 emu/cm³ respectively, which are in agreement with the values observed by the VSM technique.

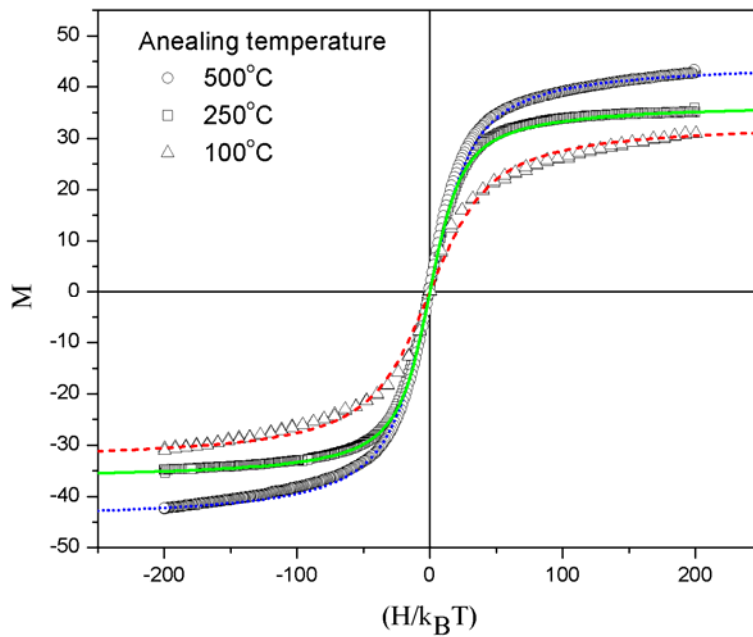


Fig. 10 shows M versus $H/k_B T$ for films annealed at temperatures of 100°C, 250°C, and 500°C with fitted Langevin function.

Conclusions

In conclusion, the vapors of NH₃, PVA concentration and annealing temperature have been found to play an important role in surface morphology/size of nanoparticles of the film. The roughness of film surface increases with the increase of exposure to NH₃ vapor due to the aggregation of the nanoparticles. The size of the α -Fe₂O₃

nanoparticles inside the films can also be controlled by varying the annealing temperature and concentration of PVA inside the solution; this has many valuable applications such as in solar cells, Li-ion batteries, and gas sensors. The method presented here is a novel approach to control the thickness of the α -Fe₂O₃ film. The film formed on the solution surface can be transferred to any desired substrate. The films are superparamagnetic in nature.

Acknowledgements

This work was partly supported by the National Research Foundation of Korea (NRF) grant funded by the Korean government (MEST) (No. 2012-0005656) and by the Research Grant for Nanotechnology Lab, Jaypee University of Information Technology, Wazirpur, Solan (India).

References

- Ahmmad B, Kusumoto Y, Abdulla-Al-Mamun M, Mihata A, Yang H (2009) Effect of single wall nanotubes as counter electrode on laser deposited Fe₂O₃ and TiO₂ films solar cells. *J Sci Res* 1:430-437
- Aronniemi M, Lahtinen J, Hautojärvi P (2004) Characterization of iron oxide thin films. *Surf Interface Anal* 36:1004-1006
- Aronniemi M, Saino J, Lahtinen J (2008) Characterization and gas sensing behavior of an iron oxide thin film prepared by atomic layer deposition. *Thin Solid Films* 516:6110-6115
- Bhowmik RN, Nagarajan R, Raganathan R (2004) Magnetic enhancement in antiferromagnetic nanoparticle CoRh₂O₄. *Phys Rev B* 69:054430-5
- Bhowmik RN, Saravanan A (2010) Surface magnetism, Morin transition and magnetic dynamics in antiferromagnetic α -Fe₂O₃ (hematite) nanograins. *J Appl Phys* 107:053916-10
- Birkholz M, Lichtenberger D, Hfpfner C, Fiechter S (1992) Sputtering of thin pyrite films. *Sol Energy Mater Sol Cells* 27:243-251
- Cesar I, Kay A, Martinez JAG, Gratzel M (2006) Translucent thin film Fe₂O₃ photo anodes for efficient water splitting by sun light: Nanostructure-directed effect of Si doping. *J Am Chem Soc* 128:4582-4583
- Chandra V, Park J, Chun Y, Lee JW, Hwang IC, Kim KS (2010) Water-dispersible magnetite-reduced graphene oxide composites for arsenic removal. *ACS nano* 4:3979-3986
- Chatzitheodorou G, Fiechter S, Kfienkamp R, Kunst M, Jaegermann W, Tributschthin H (1986) Photo active FeS₂ (pyrite) films. *Mater Res Bull* 21:1481-1487
- Chirita M, Grozescu I (2009) Fe₂O₃-nanoparticle, physical properties and their photochemical and photoelectrochemical application. *Chem Bull "POLITEHNICA" Univ (Timisoura)* 54:1-8
- Dong Q, Yin S, Guo CS, Li HH, Kumada N, Takei T, Yonesaki Y, Kinomura N, Sato T (2012) Preparation of α -Fe₂O₃ particles with controlled shape and size via a facile hydrothermal route. *JPCS* 339:012004
- Fu YY, Wang RM, Xu J, Chen J, Yan Y, Narlikar AV, Zhang H (2003) Synthesis of large arrays of aligned α -Fe₂O₃ nanowires. *Chem Phys Lett* 379:373-379

- Ge S, Shi XY, Sun K, Li CP, Uber C, Baker JR, Banaszak Holl Jr MM, Orr BG (2009) Facile hydrothermal synthesis of iron oxide nanoparticles with tunable magnetic properties. *J Phys Chem C* 113:13593-13599
- Glasscock JA, Barnes PRF, Plumb IC, Savvides N (2007) Enhancement of photoelectrochemical hydrogen production from hematite thin films by the introduction of Ti and Si. *J Phys Chem C* 111:16477-16488
- Glasscock JA, Barnes IC, Plumb IC, Bendavid A, Martin PJ (2008) Structural, optical and electrical properties of undoped polycrystalline hematite thin films produced using filtered arc deposition. *Thin Solid Films* 516:1716-1724
- Gou X, Wang G, Park J, Liu H, Yang J (2008) Monodisperse hematite porous nanospheres: synthesis, characterization, and application for gas sensors. *Nanotechnology* 19:125606
- Hwang IC, Kumar R, Kim ND, Chun Y, Lee JW, Kumar P, Mana RS, Choi C, Lee JR, Kim KS (2009) Controlling metal nanotoppings on the tip of silicide nanostructure. *Nanotechnology* 20:245605
- Jia CJ, Sun LD, Yan ZG, You LP, Luo F, Han XD, Pang YC, Zhang Z, Yan CH (2005) Single crystalline iron oxide nanotubes. *Angew Chem Int Ed* 44:4328-4333
- Jin YH, Deok S, Shim HW, Park KS, Kim DW (2012) Synthesis of core/shell spinel ferrite/carbon nanoparticles with enhanced cycling stability for Lithium ion battery anodes. *Nanotechnology* 23:125402
- Kay A, Cesar I, Gratzel M (2006) New Benchmark for water photooxidation by nanostructured α -Fe₂O₃ films. *J Am Chem Soc* 128:15714-15721
- Kim JY, Jun H, Hong SJ, Kim HG, Lee JS (2011) Charge transfer in iron oxide photoanode modified with carbon nanotubes for photoelectrochemical water oxidation: An electrochemical impedance study. *Int J Hydrogen Energ* 36:9462-9468
- Kumar R, Gautam S, Hwang IC, Lee JR, Chae KH, Thakur N (2009) Preparation and characterization of α -Fe₂O₃ polyhedral nanocrystals via annealing technique. *Mater Lett* 63:1047-1050
- Lin H, Watanabe Y, Kimura M, Hanabusa K, Shirai H (2003) Preparation of magnetic poly(vinyl alcohol) (PVA) materials by *In situ* synthesis of magnetite in a PVA matrix. *J Appl Polym Sci* 87:1239-1247
- Lindgren T, Wang H, Beermann N, Vayssieres L, Hagfeldt A, Lindquist SE (2002) Aqueous photoelectrochemistry of hematite nanorod arrays. *Sol Energy Mater Sol Cells* 71:231-243
- Liu Y, Sun D (2007) Effect of CeO₂ doping on catalytic activity of Fe₂O₃/ γ -Al₂O₃ catalyst for catalytic wet peroxide of azo dyes. *J Hazard Mater* 143:448-454
- Liu Z, Sha J, Yang Q, Su Z, Zhang H, Yang D (2007) Flower-like silicon nanostructures. *Physica E* 38:27-30
- Liu ZL, Liu CC, Yao KL, Liu PD, Ning Q (2007) Preparation and characterization of micron-sized magnetic microspheres by one-step suspension polymerization. *J Appl Polym Sci* 105:1331-1335
- Mahapatra SK, John SE, Banerjee S, Mishra M (2009) Water photooxidation by smooth and ultrathin α -Fe₂O₃ nanotubes arrays. *Chem Matters* 21:3048-3055
- Mansilla M V, Zysler R, Fiorani D, Suber L (2002) Annealing effect on magnetic properties of acicular hematite nanoparticles. *Physica B* 320:206-209
- Mathur S, Sivakov V, Shen H, Barth S, Cavelius C, Nilsson A, Kuhn P (2006) Nanostructured film of iron, tin and titanium oxide by chemical vapor deposition. *Thin Solid Films* 502:88-93

- Miller EL, Paluselli D, Marsen B, Rocheleau RE (2004) Low temperature reactivity sputtered iron oxide for thin film devices. *Thin Solid Films* 466:307-313
- Mulmudi HK, Mathews N, Dou XC, Xi LF, Pramana SS, Lam YM, Mhaisalkar SG (2011) Controlled growth of hematite (α -Fe₂O₃) nanorod array on fluorine doped tin oxide: synthesis and photoelectrochemical properties. *Electrochem Commun* 13:951-954
- Morishita N, Malagami H, Morishita R, Takeda S, Mishima F, Terazono B, Nishijima S, Kaneda Y, Tanaka N (2005) Magnetic nanoparticles with surface modification enhanced gene delivery of HVJ-E vector. *Biochem Biophys Res Commun* 334:1121-1126
- Omi S, Kanetaka A, Shimamori Y, Supsakulchai A, Nagai M, Ma GH (2001) Magnetite (Fe₃O₄) microcapsules prepared using a glass membrane and solvent removal. *J Microencapsul* 18:749-765
- Park CD, Walker J, Tannenbaum R, Stiegman AE, Frydrych J, Machala L (2009) Sol-gel derived iron oxide thin films on silicon: surface properties and interfacial chemistry. *ACS Appl Mater Interfaces* 1:1843-1846
- Parvin K, Ma J, Ly J, Sun XC, Nikles DE, Sun K, Wang LM (2004) Synthesis and magnetic properties of monodisperse Fe₃O₄ nanoparticles. *J Appl Phys* 95:7121-7123
- Pastor JM, Pérez-Landazalol JI, Gómez-Polo C, Recarte V, Larumbe S, Santamarta R, Silva MF, Pineda EAG, Hechenleitner AAW, Lima MK (2012) Entropy change linked to the magnetic field induced Morin transition in hematite nanoparticles. *Appl Phys Lett* 100:063102
- Ramachandran B, Ramachandra Rao MS, (2007) Optical and magnetic properties of monodispersed α -Fe₂O₃ nanoparticle aggregates. *AIP Conf Proc* 1003:91-93
- Ryu HS, Kim JS, Guo Z, Liu H, Kim KW, Ahn JH, Ahn HJ (2010) Electrochemical properties of Fe₂O₃ thin film fabricated by electrostatic spray deposition for lithium-ion batteries. *Phys Scr* T139:014066
- Sahoo SK, Agarwal K, Singh AK, Polke BG, Raha KC (2010) Characterization of γ - and α -Fe₂O₃ nanopowder synthesized by emulsion precipitation-calcination route and rheological behavior of α -Fe₂O₃. *IJEST* 8:118-126
- Shen S, Kronawitter CX, Jiang J, Mao SS, Guo L (2012) Surface tuning for promoted charge transfer in hematite nanorod arrays as water-splitting photoanodes. *Nano Res* 5:327-336
- Shinde SS, Bansode RA, Bhosale CH, Rajpure KY (2011) Physical properties of hematite α -Fe₂O₃ thin films: application to photo electrochemical solar cells. *J semicond* 32:013001-8
- Singh CP, Bindra KS, Bhalera GM, Oak SM (2008) Investigation of optical limiting in iron oxide nanoparticles. *Opt Express* 16:8440- 8450
- Sivako V, Petersen C, Daniel C, Shen H, Mucklich F, Mathur S (2005) Laser induced local and periodic phase transformations in iron oxide thin films obtained by chemical vapour deposition. *Appl Surf Sci* 247:513-517
- Turkovoć A, Ivanda M, Bitenc M, Orel ZC (2011) Influence of Lithium on nanosized film of Fe₂O₃. *J Nanomater* 967307:1-8
- Uekawa N, Kaneko N (1998) Nonstoichiometric properties of nanoporous iron oxide films. *J Phys Chem B* 102:8719-8724.

- Wu C, Yin P, Zhu X, Yang CO, Xie Y (2006) Synthesis of hematite (α -Fe₂O₃) nanorods; Diameter size and shape effect on their application in magnetism, Lithium ion battery and gas sensors. *J Phys Chem B* 110:17806-17812
- Zang Z, Hossain MF, Miyazaki T, Takahashi T (2010) Gas phase photocatalytic activity of ultrathin Pt layer coated on α -Fe₂O₃ films under visible light illumination. *Environ Sci Technol* 44:4741-4746
- Zhang J, Liu X, Wang L, Yang T, Guo X, Wu S, Wang S, Zhang S (2011) Synthesis and gas sensing properties of α -Fe₂O₃ @ ZnO core-shell nanospindles. *Nanotechnology* 22:185501
- Zhou HS, Mito A, Kundu D, Honma I (2000) Nonlinear optical susceptibility of Fe₂O₃ thin film synthesized by a modified sol-gel method. *J Sol-Gel Sci Technol* 19:539-541